

An Augmentation of Abrams' Law: Correlate Compressive Strength with Water-binder Ratio of Concrete Containing Fly Ash



Chenhui Jiang^{1,*}

¹Department Construction Engineering, Zhejiang College of Construction, Hangzhou, China

Abstract:

Introduction/Objective: The study presents an augmented form of Abrams' law that describes the relationship between the strength and water-binder ratio of concrete. This augmentation permits the prediction of the compressive strength of concrete containing fly ash regardless of the mass substitutions of cement by fly ash and the testing age within the ranges of 14-120 days.

Methods: In the modified Abrams' law, the (apparent) water-binder ratio is replaced by the effective one in which the reactivity of fly ash is considered, and the substitution ratio of fly ash is included. The empirical parameters in the augmented formula have been determined with multi-linear regression analysis based on experimental data.

Results: The goodness of the curve fitting to this renewed strength formula is excellent. The compressive strength predicted from the augmentation coincides with its measured counterpart in the literature.

Discussion: Abrams' law is augmented by introducing effective water-binder ratio and fly ash replacement rate, and verifies it through regression analysis of experimental and literature data. This topic has practical significance and contributes to the mixture design of sustainable concrete.

Conclusion: The Abrams' formula is basically simple but has restricted limits of validity. The proposed augmentation improves the accuracy of the strength estimation of sustainable concrete mixtures batched with mineral admixtures such as fly ash.

Keywords: Concrete, Fly ash, Abrams' law, Water-binder ratio, Compressive strength, Regression analysis.

© 2026 The Author(s). Published by Bentham Open.

This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International Public License (CC-BY 4.0), a copy of which is available at: <https://creativecommons.org/licenses/by/4.0/legalcode>. This license permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

*Address correspondence to this author at the Department Construction Engineering, Zhejiang College of Construction, Hangzhou, China; E-mail: 898238366@qq.com

Cite as: Jiang C. An Augmentation of Abrams' Law: Correlate Compressive Strength with Water-binder Ratio of Concrete Containing Fly Ash. *Open Civ Eng J*, 2026; 20: e18741495439121. <http://dx.doi.org/10.2174/0118741495439121260414095419>



Received: September 12, 2025
Revised: November 19, 2025
Accepted: November 26, 2025
Published: April 17, 2026



Send Orders for Reprints to
reprints@benthamscience.net

1. INTRODUCTION

Compressive strength is the most commonly used property for characterizing the performance of concrete materials [1]. It is safe to say that modern concrete technology began with the recognition of the relationship between compressive strength and the water-cement (binder) ratio about one hundred years ago [2, 3]. In general, the compressive strength of a structural concrete is controlled by the strength of its cementing part, *i.e.*, hardened cement paste. The latter is strongly dependent on its porosity. In turn, the (capillary) porosity is a function of the ratio of the quantity of free water involved in the paste

portion of the fresh concrete to the quantity of cement in it, *i.e.*, water-cement ratio [2]. In the modern concrete industry, the water-cement ratio is often replaced by the water-binder ratio as supplementary cementitious materials such as fly ash, ground granulated blast furnace slag, and silica fume are widely utilized.

Numerous empirical formulas have been developed to express the relationship between strength and the water-cement ratio, also known as strength formulas. Among them, Abrams' formula, which was recommended by Duff Abrams in 1918 [4, 5], is a well-known example. Consequently, the relationship between strength and water-cement

ratio is usually referred to as Abrams' law [2, 3]. These formulas estimate concrete strength based solely on the water-cement ratio, and are generally simple and straightforward, but have specific scopes and conditions of application. For example, Iqbal *et al.* [6] stated that Abrams' law has limitations when applied to concrete containing admixtures. Hedegaard and Hansen [7] doubted that Abrams' law is incompatible with concrete mixtures containing fly ash. Bhanja and Sengupta [8] confirmed that Abrams' law is not directly applicable to silica fume concretes. The original formula should be properly modified and/or augmented.

Fly ash, a byproduct of coal-fired power plants, is well accepted as a pozzolanic material that can be used either as a component of blended Portland cements or as a mineral admixture in concrete. There are beneficial effects on workability and durability with a replacement ratio of cement by fly ash on the order of 25%-30%, while with 50% or more cement replaced by fly ash, it is possible to produce sustainable, high-performance concrete that shows high workability, high long-term strength, and high durability [9, 10]. Higher Volumes (*e.g.*, up to 50%) of Fly Ash (HVFA) have been successfully used for specific structural applications. In some specific cases, structural concrete has been batched with up to 80% fly ash. For flowable fill and low-density applications, concrete mixtures with up to 90% fly ash have been developed. It should be noted that for particularly reactive fly ashes, it is possible to produce acceptable concrete with 100% fly ash. While HVFA has a wide range of benefits, possibly the most attractive property of all is durability. In addition, HVFA is considered an important sustainability measure in the concrete industry.

Despite all the criticisms of Abrams' law, the water-cement ratio still remains the single most important factor that influences strength development in concrete, where cement is the only cementitious material. According to the current knowledge, the accuracy of applying the water-cement ratio law to concrete with fly ash and silica fume has not been thoroughly verified. Concrete mixes are proportioned so that the desired strengths are obtained at specified ages. To date, the most influential factor on strength development appears to be the water-cementitious material ratio. When the cementitious material is composed of more than cement, the water-cement ratio law may not be an adequate basis for mix proportioning. This study investigates the applicability of the water-cement ratio law to concrete containing fly ash. A substitute water-cementitious material ratio law is proposed to recognize the cementing properties of admixtures such as fly ash. This modified water-cementitious material law is necessary for improved concrete mix design.

In order to accurately predict the compressive strength of concrete containing fly ash with different dosages, this work augments Abrams' law to extend its applicability. A new compressive strength formula based on the original Abrams' law is proposed in this paper. The formula has a second independent variable other than the water-binder ratio. Meanwhile, considering the time-dependent reactivity of fly ash, (apparent) water-binder ratios are replaced by

effective ones at various ages. The augmented strength formula contains three empirical parameters that are solved with multi-linear regression analysis based on measured strength data. The measured data come from 40 concrete mixtures with various water-binder ratios (ranging from 0.29 to 1.00) and mass substitution ratios (ranging from 0% to 80%) of fly ash. Experimental data in previous literature are utilized to validate the augmented form of Abrams' law in terms of fly ash concrete.

2. DATA AND METHODS

2.1. Evolution and Augmentation of Abrams' Law

Duff Abrams initially expressed the relationship between the strength of concrete and its water-cement ratio (0.30 to 1.20) [2-6] defined as Eq. (1):

$$f_c = \frac{K_1}{K_2^{W/C}} \quad (1)$$

where, f_c is compressive strength (MPa), W/C is water-cement ratio by weight (W and C are weights of water and cement, respectively), and K_1 , K_2 are empirical parameters that are independent of the strength and water-cement ratio of concrete but may be a function of the units, type of cement, aggregate and admixture used, methods of making, curing and testing the specimen, age at testing, and type of strength [3]. It can be transformed into Eq. (2):

$$\ln(f_c) = K_3 - K_4 \cdot (W/C) \quad (2)$$

Similarly, in Eq. (2), K_3 and K_4 are also empirical parameters that can be resolved by regression analysis. It is worth noting that Abrams' law is very similar to Bolomey's equation [11], which has served as the basis for practical concrete mixture proportioning in many European countries [2] and in China for more than 70 years.

Popovics and Ujhelyi [2] have generalized the basic form Eq. (1): of Abrams' law to account for the fineness and composition of Portland cement, as well as the testing age. Despite its simplicity, it can reproduce the effects of types and properties of cements on strength development. According to Iqbal *et al.* [6], the applicability of Abrams' law is poor for ready-mixed concrete that includes many more variables than trial mixtures. The law has limitations with concrete containing chemical admixtures that modify pore structures (*e.g.*, air-entraining agents). The authors have made modifications to Abrams' law by replacing w/c with water plus the volume of entrained air. This improves the accuracy of strength prediction to some extent.

Nagaraj and Banu [12] have generalized Abrams' law in the form of Eqs. (3 and 4), respectively:

$$f_c = [-0.2 + 0.6/(W/C)] \cdot f_{c,W/C=0.5} \quad (3)$$

(For $f_{c,W/C=0.5} > 30$ MPa)

$$f_c = [-0.73 + 0.865/(W/C)] \cdot f_{c,W/C=0.5} \quad (4)$$

(For $f_{c,W/C=0.5} \leq 30$ MPa)

in which, $f_{c,w/c=0.5}$ is compressive strength (MPa) when $w/c = 0.5$. This is equivalent to the reference state to reflect the synergetic effects between constituents of concrete [9, 12]. As stated by Rao [13], Abrams' law for cement mortars has been formulated with Eqs. (5 and 6):

$$f_c = \alpha \cdot (W/C)^\beta \quad (5)$$

$$f_c = \alpha \cdot [1/(W/C) + \beta] \quad (6)$$

where α and β are constants in terms of test data. It has been observed that the Abrams' generalized law is applicable to mortars with W/C greater than 0.40.

Although a great deal of experimental data supports Abrams' law within practical limits, further analysis indicates that Eqs. (1-6) and other comparable formulas with water-cement ratio as the single independent variable, are correct only as a first approximation [2, 5, 12]. These previous formulas cannot accurately reflect many factors influencing the strength of modern concrete, especially the addition of mineral and chemical admixtures. This has been verified by many experimental evidences [2, 3, 6-8, 14]. Therefore, augmented formulas for strength estimation are needed that include additional variables related to the characteristics of modern concrete composition. As an attempt, the authors introduced the mass substitution ratio of cement by fly ash (FA/B) as a second variable and augmented Eqs. (1 into 7) to correlate the f_c of fly ash concrete with its effective water-binder ratio:

$$f_c = \frac{K_1}{K_2^{[W/(C+\mu \cdot FA)+(FA/B)]}} \quad (7)$$

where FA is the quantity of fly ash. B stands for the total weight of binding materials, herein $B = C+FA$. μ is a factor of pozzolanic reactivity (or cementing efficiency [7, 15]) of fly ash. $W/(C+\mu \cdot FA)$ is the effective water-binder ratio, while $W/(C+FA)$ presents the apparent water-binder ratio. This resolves to Eq. (8):

$$\ln f_c = k_1 - k_2 \cdot \left(\frac{W}{C + \mu \cdot FA} \right) - k_3 \cdot \left(\frac{FA}{B} \right) \quad (8)$$

in which, k_1 , k_2 and k_3 are empirical parameter. They will be determined with regression analysis in the remainder of this paper.

By multiplying the reactivity factor μ , the weight of fly ash can be transformed into the equivalent weight of cement. According to Mondal and Bhanja [14], the value of μ for any concrete varies from close to zero at very early ages to 0.9 after 3-10 years. After a thorough evaluation, 0.25 and 0.22 were recommended as the average values of μ at the ages of 28 days and 7 days [12, 15]. In this study, 0.15, 0.20, 0.24, and 0.30 are assigned to μ as its values at the ages of 14 days, 28 days, 60 days, and 120 days, respectively.

2.2. Materials

Two types of Portland cement (C-I and C-II) were used. C-I is a sulphate-resistant Portland cement. It is somewhat similar to ASTM type IV cements. C-II is an ordinary Portland cement with higher C_3A and C_4AF contents. It is similar to ASTM Type I cements. None of the cements used contained fly ash as received from the suppliers. Chemical compositions of the two cements are tabulated in Table 1. Two different fly ashes (FA-I and FA-2) were used. Both are commercially available in China and are from different suppliers. Chemical compositions, specific gravity, and Blaine fineness of the fly ash are also listed in Table 1. Crushed stone with a maximum nominal size of 16 mm and river sand were used as coarse and fine aggregates, respectively. A liquid polycarboxylate-based superplasticizer is also used to regulate the workability of fresh mixtures.

2.3. Mixture Proportions

Mixture proportions of a total of 40 concretes in the four series of different cement-fly ash combinations (*i.e.*, C-I-FA-I, C-I-FA-II, C-II-FA-I, and C-II-FA-II) are presented in Table 2. The mixtures without the addition of fly ash can be defined as the control mixtures (*i.e.*, Ctrl-C-I and Ctrl-C-II). For some mixtures which were particularly rich in binders, it was necessary to introduce proper dosages of superplasticizer to achieve fresh concrete slump values of 70-100 mm, which is required for all mixtures. However, the main parameters in the investigations, which are water-binder ratios and substitution ratios of fly ash by weight, were carefully maintained on the basis of free water content even when additives were used. The ranges of apparent water-binder ratios and substitution ratios of fly ash are 0.29-1.00 and 0%-80%, respectively.

Table 1. Oxide composition and physical properties of cements and fly ashes.

Items	C-I	C-II	FA-I	FA-II
SiO ₂ (%)	24.51	19.63	52.67	64.25
Al ₂ O ₃ (%)	2.41	2.13	31.27	22.39
Fe ₂ O ₃ (%)	2.76	2.13	5.47	6.25
CaO (%)	66.38	63.54	3.38	2.73
MgO (%)	0.61	3.16	1.24	1.66
SO ₃ (%)	2.26	2.73	0.25	0.53
¹ LOI (%)	0.76	2.13	2.45	2.87
² Potential typical mineral compounds				
C ₂ S (%)	21.95	13.83	---	---
C ₃ S (%)	64.05	58.17	---	---
C ₃ A (%)	2.06	13.58	---	---
C ₄ AF (%)	7.79	6.94	---	---

(Table 3) contd....

Items	C-I	C-II	FA-I	FA-II
Specific gravity	3.08	3.16	2.23	2.27
³ Blaine fineness (m ² /kg)	376	368	388	349

Note: ¹LOI stands for loss on ignition; ²Calculated with Bogue's equation [16], C₂S = 2CaO·SiO₂, C₃S = 3CaO·SiO₂, C₃A = 3CaO·Al₂O₃ and C₄AF = 4CaO·Al₂O₃·Fe₂O₃, ³Test by the Blaine air permeability method.

Table 2. Mixture proportions of concrete.

Mixture No.	¹ W/B	² FA/B	Unit Contents of Constituent Materials (kg/m ³)						Mixture No.	W/B	FA/B	Unit Contents of Constituent Materials (kg/m ³)					
			³ W	⁴ C	⁵ FA	⁶ S	⁷ G	⁸ SP				W	C	FA	S	G	SP
Ctrl-C-I-01	1.00	---	200	200	---	863	1054	---	Ctrl-C-II-01	1.00	---	200	200	---	846	1060	---
Ctrl-C-I-02	0.71	---	195	273	---	744	1156	---	Ctrl-C-II-02	0.71	---	195	273	---	732	1116	---
Ctrl-C-I-03	0.56	---	195	351	---	677	1134	---	Ctrl-C-II-03	0.56	---	195	351	---	670	1147	---
Ctrl-C-I-04	0.45	---	195	429	---	618	1126	---	Ctrl-C-II-04	0.45	---	193	425	---	607	1122	---
Ctrl-C-I-05	0.38	---	195	507	---	583	1077	1.17	Ctrl-C-II-05	0.38	---	195	507	---	565	1096	---
C-I-FA-I-01	0.71	0.57	175	105	140	711	1142	---	C-II-FA-I-01	0.71	0.57	176	106	141	696	1180	---
C-I-FA-I-02	0.56	0.67	180	108	216	643	1137	---	C-II-FA-I-02	0.56	0.67	176	106	211	624	1168	---
C-I-FA-I-03	0.45	0.73	180	108	288	582	1083	1.54	C-II-FA-I-03	0.45	0.73	180	108	288	562	1126	1.27
C-I-FA-I-04	0.38	0.77	180	108	360	543	1159	---	C-II-FA-I-04	0.38	0.77	176	106	352	524	1099	3.34
C-I-FA-I-05	0.71	0.29	180	180	72	742	1173	---	C-II-FA-I-05	0.71	0.29	180	180	72	721	1166	---
C-I-FA-I-06	0.56	0.44	180	180	144	657	1137	---	C-II-FA-I-06	0.56	0.44	176	176	141	650	1191	---
C-I-FA-I-07	0.45	0.55	180	180	216	578	1082	1.11	C-II-FA-I-07	0.45	0.55	180	180	216	577	1136	---
C-I-FA-I-08	0.38	0.62	180	180	288	557	1049	3.09	C-II-FA-I-08	0.38	0.62	180	180	288	531	1097	2.11
C-I-FA-I-09	0.33	0.67	180	180	360	517	1167	---	C-II-FA-I-09	0.33	0.67	180	180	360	490	1052	3.83
C-I-FA-I-10	0.56	0.22	180	252	72	685	1139	---	C-II-FA-I-10	0.56	0.22	176	246	70	660	1174	---
C-I-FA-I-11	0.45	0.36	180	252	144	613	1099	1.27	C-II-FA-I-11	0.45	0.36	180	252	144	593	1147	---
C-I-FA-I-12	0.38	0.46	180	252	216	566	1066	3.28	C-II-FA-I-12	0.38	0.46	180	252	216	544	1110	1.68
C-I-FA-I-13	0.33	0.53	180	252	288	525	1014	6.53	C-II-FA-I-13	0.33	0.53	176	246	282	509	1082	4.17
C-I-FA-I-14	0.29	0.59	180	252	360	477	1147	---	C-II-FA-I-14	0.29	0.59	180	252	360	465	1017	7.16
C-I-FA-I-15	0.45	0.18	180	324	72	645	1116	0.79	C-II-FA-I-15	0.45	0.18	180	324	72	611	1155	0.99
C-I-FA-I-16	0.38	0.31	180	324	144	575	1084	3.46	C-II-FA-I-16	0.38	0.31	180	324	144	558	1122	2.06
C-I-FA-I-17	0.33	0.40	180	324	216	534	1035	6.21	C-II-FA-I-17	0.33	0.40	176	317	211	520	1096	3.64
C-I-FA-I-18	0.29	0.47	180	324	288	476	1117	1.84	C-II-FA-I-18	0.29	0.47	176	317	282	484	1048	7.97
C-I-FA-I-19	0.38	0.15	180	396	72	601	1985	2.53	C-II-FA-I-19	0.38	0.15	180	396	72	572	1135	2.62
C-I-FA-I-20	0.33	0.27	180	396	144	559	1170	---	C-II-FA-I-20	0.33	0.27	176	387	141	534	1108	3.85
C-I-FA-II-01	0.71	0.57	180	108	144	694	1176	---	C-II-FA-II-01	0.71	0.57	180	108	144	696	1169	---
C-I-FA-II-02	0.56	0.67	175	105	210	628	1132	---	C-II-FA-II-02	0.56	0.67	176	106	211	628	1171	---
C-I-FA-II-03	0.45	0.73	180	108	288	565	1091	1.31	C-II-FA-II-03	0.45	0.73	176	106	282	573	1143	0.50
C-I-FA-II-04	0.38	0.77	180	108	360	523	1167	---	C-II-FA-II-04	0.38	0.77	176	106	352	679	1116	2.89
C-I-FA-II-05	0.71	0.29	180	180	72	724	1167	---	C-II-FA-II-05	0.72	0.28	176	176	70	725	1169	---
C-I-FA-II-06	0.56	0.44	180	180	144	639	1146	---	C-II-FA-II-06	0.56	0.44	176	176	141	645	1177	---
C-I-FA-II-07	0.45	0.55	180	180	216	580	1104	0.79	C-II-FA-II-07	0.44	0.55	176	180	216	582	1139	---
C-I-FA-II-08	0.38	0.62	180	180	288	534	1059	2.34	C-II-FA-II-08	0.38	0.62	176	176	282	542	1116	0.92
C-I-FA-II-09	0.33	0.67	180	180	360	496	1172	---	C-II-FA-II-09	0.33	0.67	176	176	352	503	1073	2.32
C-I-FA-II-10	0.56	0.22	180	252	72	659	1167	---	C-II-FA-II-10	0.56	0.22	180	252	72	658	1170	---
C-I-FA-II-11	0.47	0.36	180	245	140	604	1133	1.16	C-II-FA-II-11	0.45	0.36	176	246	141	603	1160	---
C-I-FA-II-12	0.40	0.46	180	245	210	556	1074	2.28	C-II-FA-II-12	0.39	0.46	176	246	211	553	1128	1.28
C-I-FA-II-13	0.33	0.53	180	252	288	505	1026	4.27	C-II-FA-II-13	0.33	0.53	176	246	282	513	1086	2.69
C-I-FA-II-14	0.29	0.59	180	252	360	470	1159	---	C-II-FA-II-14	0.29	0.59	176	246	352	478	1040	4.43
C-I-FA-II-15	0.45	0.18	180	324	72	613	1127	0.59	C-II-FA-II-15	0.45	0.18	176	317	70	618	1168	0.54
C-I-FA-II-16	0.38	0.31	180	324	144	560	1086	2.06	C-II-FA-II-16	0.38	0.31	176	317	141	563	1133	2.02
C-I-FA-II-17	0.33	0.40	180	324	216	518	1035	6.48	C-II-FA-II-17	0.33	0.40	176	317	211	524	1099	3.22
C-I-FA-II-18	0.29	0.47	180	324	288	478	1137	1.84	C-II-FA-II-18	0.29	0.47	176	317	282	487	1054	6.65
C-I-FA-II-19	0.38	0.15	180	396	72	575	1099	1.87	C-II-FA-II-19	0.39	0.15	176	387	70	581	1147	2.15
C-I-FA-II-20	0.33	0.27	180	396	144	529	1106	---	C-II-FA-II-20	0.33	0.27	176	387	141	535	1111	2.32

Note: ¹W/B = water-binder ratio; ²FA/B = fly ash to total binders (including cement and fly ash) ratios; ³W = water; ⁴C = cement; ⁵FA = fly ash; ⁶S = quartz sand; ⁷G = crushed granite; ⁸SP = super-plasticizer.

To improve the representation of the mix design of concrete, specific water/binder and fly ash/binder ratio ranges were chosen based on several typical databases of mixture proportions for ready-mixed concrete used in commercial reinforced concrete buildings. Considering the scope of application of the extension of Abrams' law, the mixtures with a water/binder ratio higher than 0.45 were also included. The range of fly ash/binder ratio were prescribed to cover the overwhelming majority of engineering applications in China.

2.4. Testing Procedures

Twelve 100 mm cubic specimens for compressive strength tests were fabricated from each mixture listed in Table 2. Three specimens were tested for strength in accordance with the Chinese national standard (GB 50081-2019) [17] after 14, 28, 60, and 120 days of continuous water curing at 20 °C. Immediately after casting, the cubic specimens with steel moulds were first stored in isothermal curing chambers (20 °C) for 24 hours, then stripped and placed in saturated lime water until the specific age of testing.

3. RESULTS AND DISCUSSION

Experimental data are presented that suggest that the development of strength in fly ash concretes may be due to two mechanically independent pore-filling mechanisms. One mechanism is hydration of Portland cement, and the other mechanism is due to the reaction of fly ash. Moreover, it is postulated that the traditional water/cement ratio for normal Portland cement concrete, produced without fly ash, can be modified to accommodate concrete containing FA.

For given materials, age, and curing conditions, the strength of hardened concrete is determined exclusively by the ratio of free water to Portland cement, together


with the ratio of free water to fly ash. Thus, the strength of fly ash concrete is independent of the absolute content of free water, Portland cement, and fly ash in the concrete.

When dealing with concrete, which is inherently highly variable, a coefficient of determination (R^2) above 0.95 in a regression analysis usually indicates a strong relationship between a hypothetical model of concrete and corresponding experimental data. The maximum theoretically possible R^2 value of 1.00 would indicate perfect correlation between theory and experiments. Because of unavoidable experimental scatter, R^2 values above 0.95 are rarely obtained in concrete testing. The relatively high R^2 value observed in this study may not necessarily indicate overfitting. R^2 is a measure of model fit, and the values close to 1 often indicate good performance. However, to assess overfitting, other factors to consider include model complexity, data representativeness, and validation metrics. Overfitting can occur when the model captures noise or irrelevant patterns in the training set rather than generalizable relationships. To mitigate this, techniques like cross-validation, regularization, or simplifying the model architecture can be employed.


For all four series of experimentally investigated concrete mixtures, a statistical analysis was conducted to evaluate how accurate the measured test results conform to predictions by the augmented formula of strength (*i.e.*, Eq. 8). A multilinear regression analysis, based on the least-squares method, has been used to calculate the best-fitting line and the best estimates of the empirical parameters (or constants) in each case. The analysis was performed using the MATLAB R2011b software package. All the results of regression analysis, including the values of k_1 , k_2 , and k_3 and R^2 (*i.e.*, coefficient of correlation), were listed in Table 3. For example, several 3D plots of data fitting are shown in Fig. (1a-d).

Table 3. Regression analysis results of empirical parameters in the augmented Abrams' formula.


Parameters	k_1	k_2	k_3	Coefficients of Correlation (R^2)
Mixture series: C-I-FA-I				
14 d	4.801	2.513	0.032	0.94
28 d	5.059	2.516	0.400	0.98
60 d	5.236	2.524	0.299	0.94
120 d	5.378	2.472	0.391	0.92
Mixture series: C-I-FA-II				
14 d	4.873	2.528	0.246	0.97
28 d	5.100	2.587	0.237	0.98
60 d	5.196	2.420	0.197	0.94
120 d	5.251	2.255	0.176	0.92
Mixture series: C-II-FA-I				
14 d	4.748	2.236	-0.033	0.96
28 d	4.922	2.321	-0.037	0.96
60 d	5.062	2.416	-0.039	0.96
120 d	5.157	2.427	-0.110	0.94
Mixture series: C-II-FA-II				
14 d	4.736	2.213	-0.001	0.98
28 d	4.860	2.240	-0.029	0.98
60 d	4.981	2.271	-0.118	0.97
120 d	5.013	2.230	-0.276	0.95

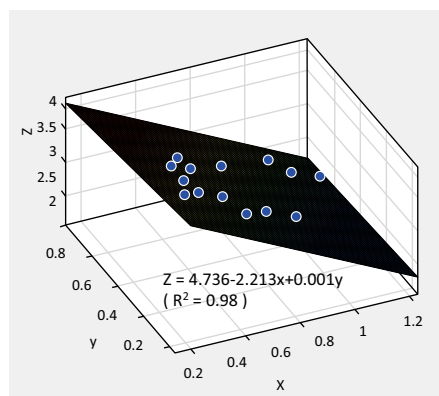


(a) Mixture series: C-II-FA-II Age: 14 d

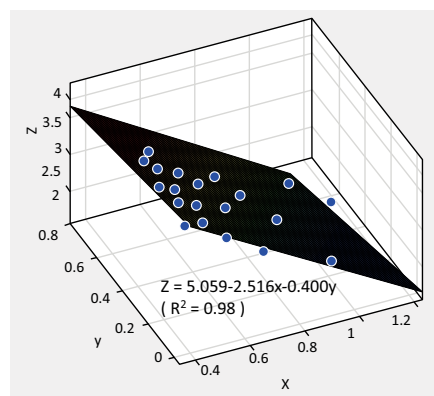

(b) Mixture series: C-I-FA-I Age: 28 d

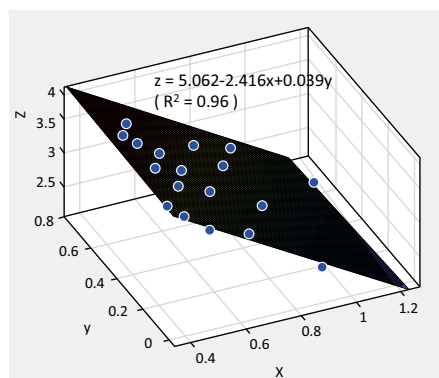

(c) Mixture series: C-II-FA-I Age: 60 d

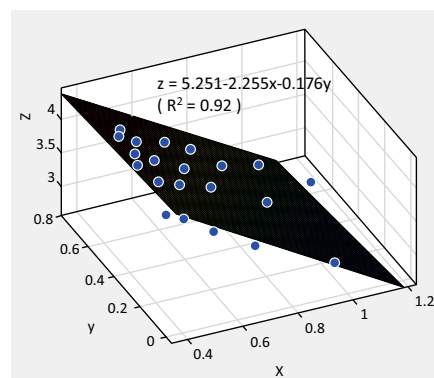

(d) Mixture series: C-I-FA-II Age: 120 d

Fig. (1a-d). Partial multi-linear regression analysis results of the augmented Abrams' formula. (In these 3D plots, x, y, and z-axis represent effective water-binder ratio, substitution ratio of fly ash, and natural logarithm of compressive strength, respectively. Blue points are the measured data. The planes are the best results of regression analysis.)

When dealing with concrete, which is inherently an extremely variable material, a coefficient of determination (R^2) above 0.95 in a regression analysis usually indicates a strong fit between a mathematical model and the corresponding measured data. Due to unavoidable experimental scatter, R^2 values above 0.95 are not readily obtained for concrete data [6, 9, 14]. Considering that most of R^2 values are at 0.95 or above (Table 3), it may be concluded that the augmented formula Eq. (8) is highly compatible with concrete mixtures containing fly ash with a wide range of dosages.

As presented in Table 3, it seems that the values of k_1 are systematically increased with the ages of strength evaluation for each series of fly ash mixtures, while the values of k_2 and k_3 change irregularly. Compared with the values of k_3 , those of k_1 and k_2 change within relatively narrow ranges. This implies that the ultimate strength and the influence of the water-binder ratio on compressive strength are unchanged across specific ages, mixture proportions, and fly ash replacement ratios. The negative values of k_3 for the mixture series of C-II-FA-I and C-II-FA-II indicate that the positive effects on the strength

development with different degrees are produced by the inclusion of fly ash.

As fly ash contributes to the strength increase with age, the value of k_3 decreases with age. Despite these results obtained from different combinations of cements and fly ashes (Table 1), the values of the three empirical parameters are slightly changed. To be honest, as an extension of Abrams' law, Eq. (8) was not rigorously mechanistically developed. Therefore, the implications of the beneficial effect of fly ash on the negative value of k_3 are not easy to interpret at this point [19].

In Fig. (1), the relationships among compressive strength, water-binder ratio, and replacement ratio of fly ash are plotted in log-linear 3D coordinate systems. The blue points represent measured compressive strength values. The planes are the best results of regression analysis. It is evident that the fitting surfaces match well with the tested data of compressive strength. Although four plots are presented here, all results of the 3D linear regression analysis of various mixture series at different ages closely match the corresponding experimental data.

To validate the applicability of the proposed augmented form of Abrams' law, the experimental compressive-strength data from the literature are compared with the predicted values. The measured data are cited from three sources on fly ash concrete [10, 13, 14]. The values of the three parameters are based on average values in Table 3. The comparisons of the predicted values and the measured data at different ages are plotted in Fig. (2a-d), respectively [10, 14, 18]. In general, the predicted compressive strength is very close

to the measured results. The augmented formula based on Abrams' law permits the prediction of compressive strength of concrete containing fly ash [19]. For the ages of 14 days and 120 days, the predicted values of compressive strength are slightly lower than their measured values. However, the opposite is true for the ages of 28 days and 60 days. Taking many differences of constituent materials and mixture proportions into account, the minor deviations between the predicted and measured values are reasonable and tolerable.

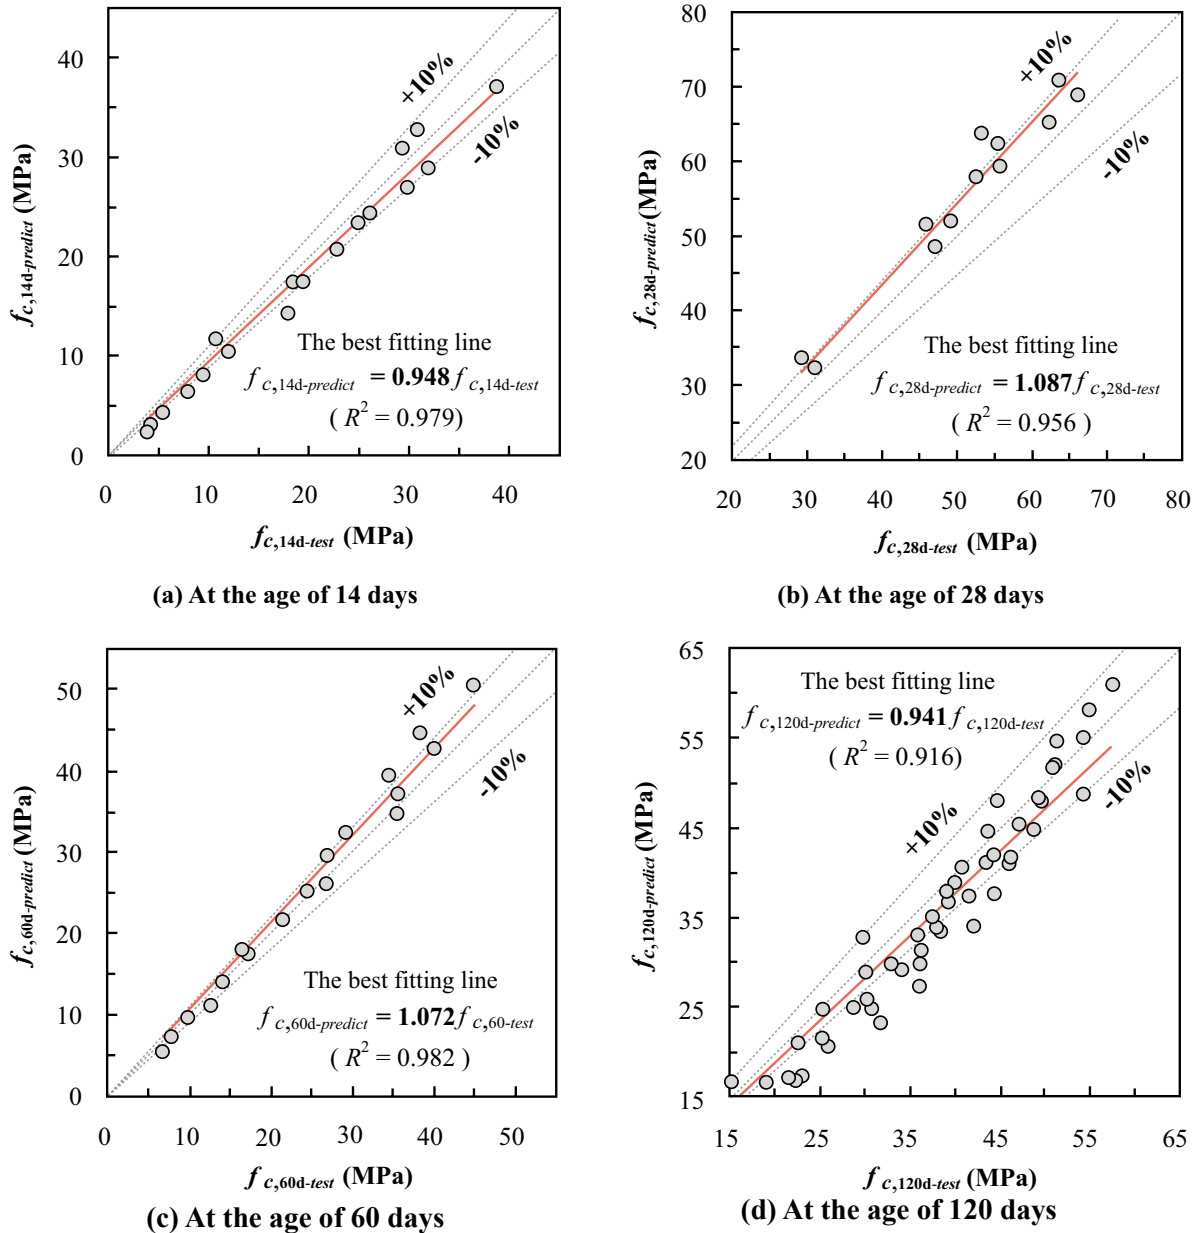


Fig. (2). Validation of the augmented form of Abrams' law on previous strength data at different ages. (In each plot, the horizontal and vertical axes stand for measured and predicted compressive strength, respectively. The measured data in (a), (b), (c), and (d) are extracted from [10, 14, 18].

Despite Abrams' law, which is considered a fundamental principle of concrete mixture proportioning is an empirical approximation other than a physical law in nature; it remains valid and useful within a relatively wide range of concrete mixture proportions. However, when fly ash from coal-fired power plants is commonly used as a mineral admixture in normal Portland cement concrete, the mixture design becomes more complex than for pure Portland cement concrete mixtures, and the original edition of Abrams' law is ineffective. In this study, an extension of Abrams' law that applies to concrete mixtures containing fly ash is formulated and demonstrated based on a series of self-designed experimental data. Notably, the relationship between mechanical strength and water-cement/binder ratio of concrete is strongly dependent on constituent materials, mixture proportions, and specific testing conditions. The parameters in the formula of the extended Abrams' law certainly vary from one testing system to another. Therefore, in order to accurately estimate compressive strength based on water-cement/binder ratio and vice versa, a sufficient quantity of experimental data that presents various conditions and their combinations must be collected and analyzed. In the current situation, maybe the AI tools can be employed to achieve the objective conveniently. The process of further developing the augmentation of Abrams' law with the aid of artificial intelligence is in progress. On the other hand, the physical mechanisms of Abrams' law and its extensions are urgently needed to be explored and interpreted. The implication of the macroscopic-scale strength-W/B relationship and the hydration kinetics/micro-structural evolution of concrete materials is a promising topic worthy of exploration. In addition, the mixture proportioning method based on Abrams' law must be updated and expanded to account for modern concrete, which contains many more components.

CONCLUSIONS

This study presents an augmentation of the famous Abrams' law correlating the strength of concrete with its water-cement ratio. The augmented strength formula can accurately predict the compressive strength of fly ash concrete. From the results of the study reported herein, the following conclusions could be drawn:

- In the proposed augmented form of Abrams' law, the mass substitution ratio of cement by fly ash is introduced as a second independent variable beside the water-binder ratio. In addition, the apparent water-binder ratio is replaced by the effective one, thereby accounting for the quantitative pozzolanic reactivity of fly ash.
- The empirical parameters (constants) in the augmented formula for compressive strength are determined by multiple linear regression analysis of experimental data. The values of these parameters change negligibly with constituent types, mixture proportions, and concrete age.
- The predicted strength from the augmented formula of Abrams' law aligns well with the measured data in previous literature. The augmentation is applicable to strength predictions of concrete with various dosages of fly ash.

AUTHOR'S CONTRIBUTION

The author confirms sole responsibility for the following: study conception and design, data collection, analysis and interpretation of results, and manuscript preparation.

LIST OF ABBREVIATIONS

HVFA	=	Higher volume fly ash
LOI	=	Loss on ignition
SP	=	Super-plasticizer
FA	=	Fly ash

CONSENT FOR PUBLICATION

Not applicable.

AVAILABILITY OF DATA AND MATERIALS

The data of current study are available from corresponding author, [C.J], on a reasonable request.

FUNDING

This research was funded by the General Scientific Research Program of the Department of Education of Zhejiang Province, grant number Y202250417, the Teaching Reform and Research Program of Zhejiang Higher Vocational Education, grant number jg20230178, General Scientific Research Program of the Department of Housing and Urban-Rural Development of Zhejiang, China Province, grant number 2024K056.

CONFLICT OF INTEREST

The author declares no conflict of interest, financial or otherwise.

ACKNOWLEDGEMENTS

The author would like to thank Xuehong Gan, Xuehui Zou, and other colleagues for their assistance in the experiment; otherwise, our experimental investigation would not have been successfully completed. Thanks to Weihao Feng and Lichong Song for their guidance in the preparation of this manuscript, which has greatly improved the language expressions and scientific rigor. I would like to express my heartfelt thanks and deep respect to them. In particular, the peer reviewers of this article are warmly acknowledged.

REFERENCES

- [1] C. Jiang, Y. Yang, T. Ni, and X. Wang, "Correlating strength of concrete to its early-age temperature rise", *Mag. Concr. Res.*, vol. 67, no. 23, pp. 1274-1286, 2015. [<http://dx.doi.org/10.1680/macrcr.14.00216>]
- [2] S. Popovics, and J. Ujhelyi, "Contribution to the concrete strength versus water-cement ratio relationship", *J. Mater. Civ. Eng.*, vol. 20, no. 7, pp. 459-463, 2008. [[http://dx.doi.org/10.1061/\(ASCE\)0899-1561\(2008\)20:7\(459\)](http://dx.doi.org/10.1061/(ASCE)0899-1561(2008)20:7(459))]
- [3] T. Meng, X. Yang, H. Wei, R. Meng, and W. Zhou, "Study of the relationship between the water binder ratio and strength of mixed recycled aggregate concrete based on brick content", *Constr. Build. Mater.*, vol. 394, p. 132148, 2023. [<http://dx.doi.org/10.1016/j.conbuildmat.2023.132148>]

- [4] D. P. Bentz, M. A. Peltz, and J. Winpigler, "Early-age properties of cement-based materials. II: Influence of water-to-cement ratio", *J. Mater. Civ. Eng.*, vol. 21, no. 9, pp. 512-517, 2009. [[http://dx.doi.org/10.1061/\(ASCE\)0899-1561\(2009\)21:9\(512\)](http://dx.doi.org/10.1061/(ASCE)0899-1561(2009)21:9(512))]
- [5] A.M. Neville, *Properties of concrete.*, 5th ed. Pearson Education Limited: Harlow, 2011, pp. 271-272.
- [6] I. Iqbal, W.B. Inqiad, T. Kasim, S. Besklubova, M.M. Adil, and M. Rahman, "Strength characterisation of fly ash blended 3D printed concrete enhanced with explainable machine learning", *Case Stud Constr Mater*, vol. 24, p. e05682, 2026. [<http://dx.doi.org/10.1016/j.cscm.2025.e05682>]
- [7] S. E. Hedegaard, and T. C. Hansen, "Modified water/cement ratio law for compressive strength of fly ash concretes", *Mater Struct*, vol. 25, pp. 273-283, 1992. [<http://dx.doi.org/10.1007/BF02472668>]
- [8] S. Bhanja, and B. Sengupta, "Modified water-cement ratio law for silica fume concretes", *Cement Concr. Res.*, vol. 33, no. 3, pp. 447-450, 2003. [[http://dx.doi.org/10.1016/S0008-8846\(02\)00977-8](http://dx.doi.org/10.1016/S0008-8846(02)00977-8)]
- [9] S. Kar, S. Das, A. Pradhan, A.K. Mandal, and S. Biswas, "Statistical interpretation of strength data for High-volume fly ash concrete - A new mix proportioning technique", *Procedia Struct. Integr.*, vol. 70, pp. 674-681, 2025. [<http://dx.doi.org/10.1016/j.prostr.2025.07.105>]
- [10] A. Durán-Herrera, C.A. Juárez, P. Valdez, and D.P. Bentz, "Evaluation of sustainable high-volume fly ash concretes", *Cement Concr. Compos.*, vol. 33, no. 1, pp. 39-45, 2011. [<http://dx.doi.org/10.1016/j.cemconcomp.2010.09.020>]
- [11] R. Kumar, S. Kumar, B. Rai, and P. Samui, "Development of hybrid gradient boosting models for predicting the compressive strength of high-volume fly ash self-compacting concrete with silica fume", *Structures*, vol. 66, p. 106850, 2024. [<http://dx.doi.org/10.1016/j.istruc.2024.106850>]
- [12] T.S. Nagaraj, and Z. Banu, "Generalization of Abrams' law", *Cement Concr. Res.*, vol. 26, no. 6, pp. 933-942, 1996. [[http://dx.doi.org/10.1016/0008-8846\(96\)00065-8](http://dx.doi.org/10.1016/0008-8846(96)00065-8)]
- [13] G.A. Rao, "Generalization of Abrams' law for cement mortars", *Cement Concr. Res.*, vol. 31, no. 3, pp. 495-502, 2001. [[http://dx.doi.org/10.1016/S0008-8846\(00\)00473-7](http://dx.doi.org/10.1016/S0008-8846(00)00473-7)]
- [14] A. Mondal, and S. Bhanja, "Augmentation of Abrams law for fly ash concrete", *Mater. Today Proc.*, vol. 65, no. part 2, pp. 644-650, 2022. [<http://dx.doi.org/10.1016/j.matpr.2022.03.204>]
- [15] F. A. Oluokun, "Fly ash concrete mix design and the water-cement ratio law", *Mater J*, vol. 91, no. 4, pp. 362-371, 1994. [<http://dx.doi.org/10.14359/4050>]
- [16] J. Zuo, and W. Hansen, "Curing and its effect on autogenous shrinkage and degree of hydration of cement-based materials with and without silica fume", *Cem. Concr. Res.*, vol. 58, pp. 113-121, 2014. [<http://dx.doi.org/10.1016/j.cemconres.2014.03.007>]
- [17] C. Wang, L. Chang, W. Chen, Y. Zhao, F. Qiu, E. Yuan, S. Zhang, and X. Li, "Test and evaluation method of compressive strength of existing concrete structures", *Case Stud. Constr. Mater.*, vol. 23, p. e05233, 2025. [<http://dx.doi.org/10.1016/j.cscm.2025.e05233>]
- [18] H.K. Lee, K.M. Lee, and B.G. Kim, "Autogenous shrinkage of high-performance concrete containing fly ash", *Mag. Concr. Res.*, vol. 55, no. 6, pp. 507-515, 2003. [<http://dx.doi.org/10.1680/macrc.2003.55.6.507>]
- [19] Z. M. Qiu, F. X. Chen, Y. Yu, Y. J. Gu, X. Wang, and Y. Wang, "Effects of water-cement ratio and particle diameter on the mechanical properties of cement paste particles", *Opt Laser Eng*, vol. 187, p. 108874, 2025. [<http://dx.doi.org/10.1016/j.optlaseng.2025.108874>]